



ADSORPTION OF PHARMACEUTICAL CONTAMINANTS FROM AQUEOUS SOLUTIONS BY USING NATURAL PLANTS AS ADSORBENTS ASSISTED BY ULTRASOUND PROCESS

Hannan Muheisen Hadi, Aseel M. Aljeboree and Ayad F. Alkaim

Department of Chemistry, College of Sciences for Girls, University of Babylon, Hilla, Iraq.

Abstract

Activated carbon (AC) as a source of natural plants (apricot stones) were using as a good adsorbent for removal of pollutants Ranitidine drug from aqueous solutions by assisted of sonicated. The results of different experiments showed that a (AC) that considered a friendly of the environment have ability to adsorb Ranitidine drug from aqueous solution. The sorption process dependent of the pH and was found the best result at pH 6.5, and the adsorption process has nearly reached equilibrium in 60 min. The experimental data are fitted well to Langmuir isotherm model, and the maximum adsorptive quantity of Ranitidine was 96.071 mg/g according to Langmuir model.

Key words : Pharmaceuticals, Ranitidine drug, Adsorption, Ultrasound, Activated carbon.

Introduction

Ranitidine is a histamine H₂-receptor antagonist which differs in chemical structure from both histamine and cimetidine (Rakesh Pahwa1 2016) Some selected physicochemical properties of amoxicillin are shown in table 1. Ranitidine is commonly employed in the management and treatment of acute duodenal ulcer disease, Zollinger-Ellison syndrome and systemic mastocytosis with gastric hypersecretion (J. G. MILLS 1997; Aljeboree and Alshirifi 2018). Ranitidine is the drug of choice in the treatment of the Zollinger-Ellison syndrome because of its increased potency and lesser effect on endocrine function compared to cimetidine. This drug is a selective, competitive histamine H₂-receptor antagonist and is utilized in the short-term treatment of active duodenal ulcers and gastric hypersecretory conditions (Rakesh Pahwal 2016; Alkaim 2017; Aljeboree 2019). activated carbon (AC) take to be among the adsorbents that have been utilize for the effective removal of drug from aqueous effluents (M. Ghaedi 2011; Enas M Alrobayi 2017; Louis Lefebvre 2018). Activated carbon, also called, carob activates, activated coal, or activated charcoal, is a form of carbon processed to have

minor, little-volume pores that increase the surface area obtainable for adsorption or chemical reactions. (Aljeboree, Alkaim *et al.* 2019; Hoppen, Carvalho *et al.* 2019). In this study, preparation activated carbon to removal/adsorption of drug Ranitidine from an aqueous water. The effects of different factors, for example amount of the activated carbon, pH solution, and concentration of the drug Ranitidine.

Materials and Methods

Determinations of Calibration Curves of ranitidine Drug

The calibration curve of different concentration of ranitidine drug were prepared in serial dilutions (10-100 mg/L). Absorbance was measured at the λ_{max} for drug and plotted against the concentration values of ranitidine (Fig. 1).

Adsorption Equilibrium Experiments

Stock solutions of the drug (1g/1000 mL) were prepared, and the range of required concentrations was made by dilutions with distilled water. The initial tested concentrations of drug were (10, 20, 30, 40, 50, 60, 70, 80,90 and 100 mg/L), The effect of initial solution pH on the drug adsorption by AC was studied at a concentration

**Author for correspondence* : E-mail: annenayad@gmail.com

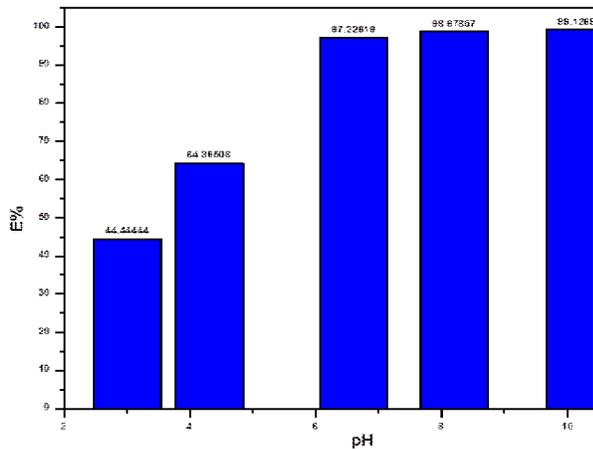


Fig. 2: Effect of solution pH on the percent removal Ranitidine drug onto (AC) initial concentration = 40 mg/L, Temp = 25°C, contact time 2 h, and mass of adsorbent 0.08 g.

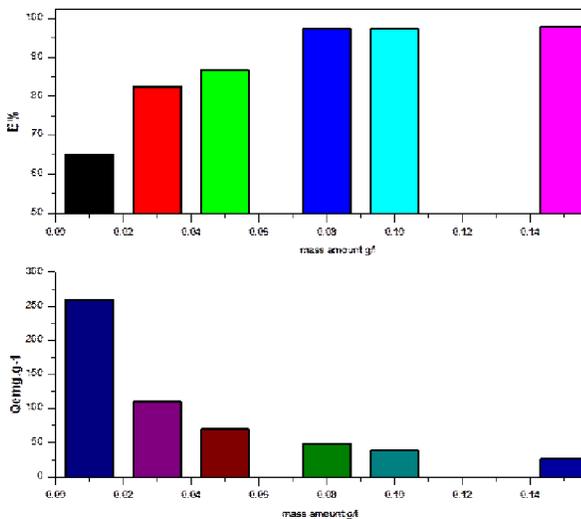


Fig. 3: Effect of mass amount of adsorbent (AC) on the percent removal and amount of adsorbed Ranitidine drug, initial concentration = 40 mg/L, Temp. = 25°C, contact time 2 h.

show in Fig. 3. percentage removal (E%) of Ranitidine drug against the mass of AC adsorbent. From Fig. 3, it is observed that the E% of adsorption is increases with increasing in the adsorbent. This might be reflected to surface area increase of the AC, that increases the binding sites. (Aljeboree and Abbas 2019; Yazidi, Atrous *et al.*, 2020; Aljeboree, Al-Gubury *et al.*, 2019).

Effect of initial dye concentration

The plot of the quantities of drug adsorbed (Qe) and (E%) drug removal versus primary concentration at several experimental conditions Fig. 4, Fig. 5. The adsorption capacity (Qe) increase with increasing initial drug concentration, while the percentage of removal decreasing with initial drug concentrations. The removal of drug by adsorption on AC was found to be rapid low

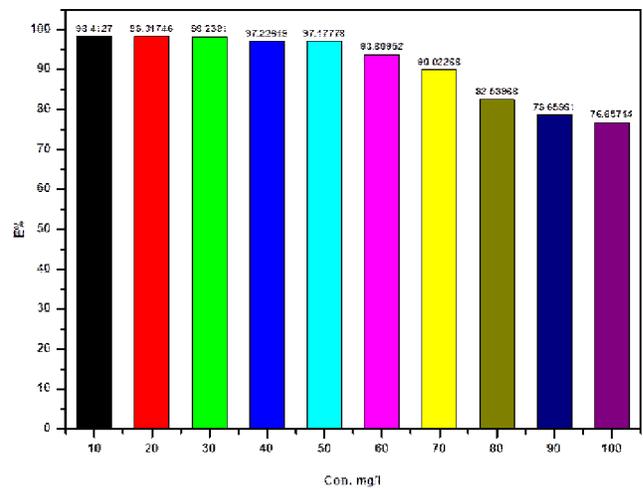


Fig. 4: Effect of initial concentration on the percent removal Ranitidine drug onto (AC) Temp = 25°C contact time

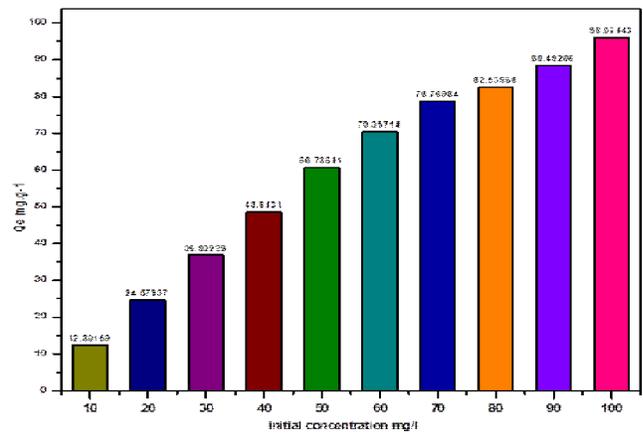


Fig. 5: Effect of initial concentration on the amount of adsorbed Ranitidine drug onto (AC) Temp. = 25°C, contact time 2 h, and mass of adsorbent 0.08 g.

concentrations of drug and then to slow down with increasing in dye concentration. the color removal of drug solution onto AC by adsorption rose rapidly at the beginning and then gradually slowed down until equilibrium was reached. It might be explained that a large number of vacant surface sites were available for adsorption during the initial stage (Fabryanty, Valencia *et al.*, 2017; Aljeboree 2019; Aljeboree, Al-Gubury *et al.*, 2019).

Effect of acid treatment on the adsorbent surfaces

The study of the effect of acid treatment on the surface was necessary to show the maximum adsorption. The adsorbent was treated by different acids such as (HNO₃, HCl, H₂SO₄). The results are illustrated in fig. 6.

It was obvious from the results shown in figures 6 the best adsorption capacity when the adsorbent treated by HNO₃, this is may be due to the increased in acid

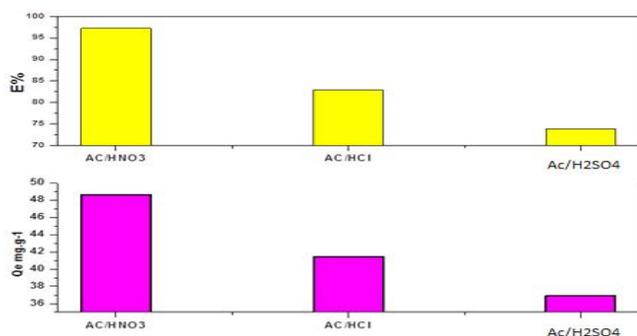


Fig. 6: Effect of different treatment on the activity of AC surface for the adsorption of drug (pH 6.5, mass adsorbent 0.08 gm).

acidity caused to re-activated the active sites for adsorbent surface (Alkaim, Zainab *et al.*, 2015).

Models of Adsorption Isotherms

Isotherm Freundlich

the isotherm Freundlich is known as equation 3 (Y.S. Ho 2002; M. Özacar 2003)

$$q_e = K_f C_e^{1/n} \tag{3}$$

q_e : adsorbent Amount adsorbed / unit mass at equilibrium (mol/g),(mg/g), C_e : the adsorbate Equilibrium scam solution next adsorption (mg/L), (mol/L), K_f : capacity factor ($L \cdot g^{-1}$), $1/n$ heterogeneity factor, n is a deviation measured of the deviation from adsorption linearity.

Its value indicates nonlinearity unit among adsorption and solution concentration as follows: adsorption route is chemical if value under to unity or it is linear if the n value equal to unity, finally the favorable physical route when value is above unity adsorption (P. Senthil Kumar 2010).

A plot of q_e versus C_e (Fig. 7) where the values of K_f and $1/n$ are obtained from the intercept and slope of the linear regressions (Table 3).

Isotherm Langmuir: it is used for the adsorption of contaminants from liquid solutions (I. Langmuir 1916; I. Langmuir 1918). Langmuir derived Other equation on the definite case of the adsorption rout nature from solution. The Langmuir adsorption isotherm was developed based that (G. Crini 2007) All accessible sites fixed number has same energy and it is available on the adsorbent surface, There was reversible Adsorption. Occurring of Monolayer adsorption. And no side communications among the adsorbates. thus Lang. adsorption isotherm is clarified in equation 4 (I. Langmuir 1916; I. Langmuir 1918)

$$q_e = \frac{q_m K_L C_e}{1 + K_L C_e} \tag{4}$$

Where q_e : adsorbed amount per unit weight at equilibrium (mg/g), C_e : con. Of adsorbent equilibrium in solution after adsorption (mg/L), q_m : the constant of Empirical Langmuir represents maximum q_e (mg/g), K_L : empirical Langmuir constant (L/mg).

The Results of this model are shown in Fig. 7, and the Langmuir constants are illustrated in table 3.

Table 3: Model of Freundlich and Langmuir isotherms parameters for Ranitidine drug adsorbed on Activated carbon (AC) at 25 °C.

| Ranitidine drug | Parameters | Isotherm models |
|-----------------|-----------------------------|-----------------|
| 92.2319±2.412 | q_m (mg.g ⁻¹) | Langmuir |
| 1.10903±0.125 | K_L (L.mg ⁻¹) | |
| 0.98009 | R^2 | |
| 44.096±3.6479 | K_f | Freundlich |
| 0.2548±0.03381 | $1/n$ | |
| 0.9003 | R^2 | |

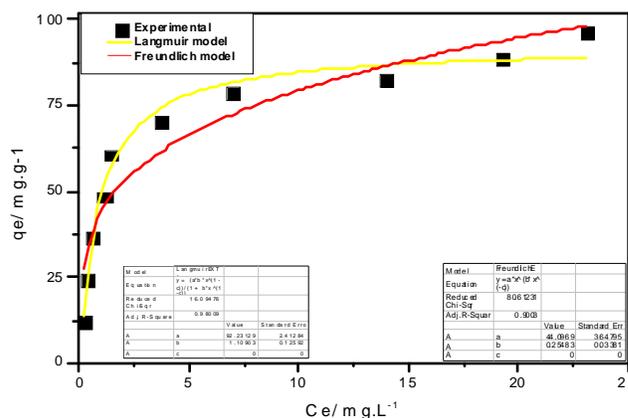


Fig. 7: Ranitidine drug adsorption model of Different adsorption isotherm nonlinear fit . on AC at mass dosage 0.08 gm, pH 6.5, 25 °C initial conc. 40mg/L.

Conclusion

1. The adsorption capacity and percentage removed increase with increasing contact time, surface area, and decreasing with increasing of adsorbent dosage
2. Optimum contact time for equilibrium to be achieved is found to be 1 hours. It is basically due to saturation of the active site which do not allow further adsorption to take place.
3. The best result have been found in pH 6.5, adsorbent dosage 0.08 gm of ACHNO₃.

References

- Aljeboree, A.M. (2019). "Removal of Vitamin B6 (Pyridoxine) Antibiotics Pharmaceuticals From Aqueous Systems By ZnO." *International Journal of Drug Delivery Technology*, **9(2)**: 125-129.
- Aljeboree, A.M. (2019). "Adsorption and Removal of pharmaceutical Riboflavin (RF) by Rice husks Activated Carbon." *International Journal of Pharmaceutical Research*, **11(2)**: 255-261.
- Aljeboree, A.M. and A.S. Abbas (2019). "Removal of Pharmaceutical (Paracetamol) by using CNT/ TiO₂ Nanoparticles." *Journal of Global Pharma Technology*, **11(01)**: 199-205.
- Aljeboree, A.M., H.Y. Al-Gubury, *et al.* (2019). "The effect of different parameters on the removal of vitamin B12 drug (as a model biochemical pollutants) by AC/clay." *Biochem. Cell. Arch.*, **19(1)**: 755-759.
- Aljeboree, A.M., A.F. Alkaim, *et al.* (2019). "Spectrophotometric Determination of Pharmaceutical by Oxidative Coupling of 4-Aminoantipyrine: A Short Review." *Journal of Engineering and Applied Sciences*, **14(2)**: 5561-5569.
- Aljeboree, A.M., A.F. Alkaim, *et al.* (2019). "Photocatalytic Degradation of Textile Dye Cristal Violet Wastewater using Zinc Oxide as a Model of Pharmaceutical Threat Reductions." *Journal of Global Pharma Technology*, **11(3)**: 138-143.
- Aljeboree, A.M. and A.N. Alshirifi (2018). "Colorimetric Determination of phenylephrine hydrochloride drug Using 4-Aminoantipyrine: Stability and higher sensitivity." *Journal of Pharmaceutical Sciences and Research*, **10(7)**: 1774-1779.
- Alkaim, A.F., Alrobay, M. Enas, Algubili, M. Abrar, Aljeboree, and M. Aseel (2017). "Synthesis, characterization, and photocatalytic activity of sonochemical/hydration-dehydration prepared ZnO rod-like architecture nano/microstructures assisted by a biotemplate." *Environmental technology*, **38(17)**: 2119-2129.
- Alkaim, A.F. and S. Zainab, *et al.* (2015). "Preparation, structure and adsorption properties of synthesized multiwall carbon nanotubes for highly effective removal of maxilon blue dye." *Korean Journal of Chemical Engineering*, **32(12)**: 2456-2462.
- Crini, G., H.N. Peindy, F. Gimbert and C. Robert (2007). "Removal of C.I. basic green 4, (malachite green) from aqueous solutions by adsorption using cyclodextrin-based adsorbent: kinetic and equilibrium studies." *Sep. Purif. Technol.*, **53**: 97-110.
- del Mar Orta, M. and J. Martn (2019). "Adsorption of propranolol onto montmorillonite: Kinetic, isotherm and pH studies." *Applied Clay Science*, **173**: 107-114.
- Enas, M., A.M.A. Alrobay, M.A. Aseel, F.A. Ayad and H.H. Falah (2017). "Investigation of photocatalytic removal and photonic efficiency of maxilon blue dye GRL in the presence of TiO₂ nanoparticles." *Particulate Science and Technology*, **35(1)**: 14-20.
- Fabryanty, R. and C. Valencia *et al.* (2017). "Removal of crystal violet dye by adsorption using bentonite – alginate composite." *Journal of Environmental Chemical Engineering*, **5**: 5677–5687.
- Ghaedi, M.A.S., H. Tavallali, F. Shojaiepoor, B. Keshavarz and H. Hossainian (2011). "Activated carbon and multiwalled carbon nanotubes as efficient adsorbents for removal of arsenazo(III) and methyl red from waste water." *Toxicol. Environ. Chem.*, **93**: 438-449.
- Hoppen, M.I. and K.Q. Carvalho, *et al.* (2019). "Adsorption and desorption of acetylsalicylic acid onto activated carbon of babassu coconut mesocarp." *Journal of Environmental Chemical Engineering*, **7(1)**: 102-862.
- Ho, Y.S., J.F. Porter and G. McKay (2002). "Individual response profiles of male Wistar rats in animal models for anxiety and depression." *Water Air Soil Pollut.*, **141**: 1-12.
- Langmuir, I. (1916). "The constitution and fundamental properties of solids and liquids. part I. Solids". *J. Am. Chem. Soc.*, **38(11)**: 2221-2295.
- Langmuir, I. (1918). "The adsorption of gases on plane surfaces of glass, mica and platinum." *J. Am. Chem. Soc.*, **40(9)**: 1361–1403.
- Mills, J.G.K.M.K., C. Webster, M. A. Sirgo, K. Fitzgerald and J.R. Wood (1997). "The safety of ranitidine in over a decade of use." *Aliment Pharmacol. Ther.*, **11**: 129–137.
- Louis Lefebvre, G.A., A. Bouzegane and D. EdouardN (2018). "Adsorption of dye with carbon media supported on polyurethane open cell foam." *Catalysis Today*, **301**: 98–103.
- Özacar, M. and Ý.A. Pengil (2003). "Adsorption of reactive dyes on calcined alunite from aqueous solutions." *J. Hazard. Mater.*, **B98**: 211–224.
- Senthil Kumar, P., S. Ramalingam, C. Senthamarai, M. Niranjana, P. Vijayalakshmi and S. Sivanesan (2010). "Adsorption of dye from aqueous solution by cashew nut shell: Studies on equilibrium isotherm, kinetics and thermodynamics of interactions." *Desalination*, **261**: 52-60.
- Rakesh Pahwal, S.S., V. Kumar and K. Kohli (2016). "Ranitidine hydrochloride: An update on analytical, clinical and pharmacological aspects". *Journal of Chemical and Pharmaceutical Research*, **7(8)**: 70-78.
- Ruwaida, A., H.Y.A.G Raheem, A.M. Aljeboree and A.F. Alkaim (2016). "Photocatalytic degradation of reactive green dye by using Zinc oxide." *Journal of Chemical and Pharmaceutical Sciences*, **9(3)**: 1134-1138.
- Yang, R. and D. Li, *et al.* "Adsorption properties and mechanisms of palygorskite for removal of various ionic dyes from water." *Applied Clay Science*, **151**: 20-28.
- Yazidi, A. and M. Atrous, *et al.* (2020). "Adsorption of amoxicillin and tetracycline on activated carbon prepared from durian shell in single and binary systems: Experimental study and modeling analysis." *Chemical Engineering Journal*, **379**: 122320.